

Prilling and Coating of Ammonium Dinitramide (ADN) Solid Green Propellant in Toluene Mixture Using Ultrasound Sonication

Citation for published version:

Rahman, A, Chin, J & Cheah, KH 2018, 'Prilling and Coating of Ammonium Dinitramide (ADN) Solid Green Propellant in Toluene Mixture Using Ultrasound Sonication', *Aerospace*, vol. 5, no. 1, 29.
<https://doi.org/10.3390/aerospace5010029>

Digital Object Identifier (DOI):

[10.3390/aerospace5010029](https://doi.org/10.3390/aerospace5010029)

Link:

[Link to publication record in Heriot-Watt Research Portal](#)

Document Version:

Publisher's PDF, also known as Version of record

Published In:

Aerospace

Publisher Rights Statement:

© 2018 by the authors. Licensee MDPI, Basel, Switzerland.

General rights


Copyright for the publications made accessible via Heriot-Watt Research Portal is retained by the author(s) and / or other copyright owners and it is a condition of accessing these publications that users recognise and abide by the legal requirements associated with these rights.

Take down policy

Heriot-Watt University has made every reasonable effort to ensure that the content in Heriot-Watt Research Portal complies with UK legislation. If you believe that the public display of this file breaches copyright please contact open.access@hw.ac.uk providing details, and we will remove access to the work immediately and investigate your claim.

Article

Prilling and Coating of Ammonium Dinitramide (ADN) Solid Green Propellant in Toluene Mixture Using Ultrasound Sonication

Asad Rahman ^{1,†}, Jitkai Chin ^{1,*,†}  and Kean How Cheah ^{2,†}

¹ Department of Chemical and Environmental Engineering, University of Nottingham Malaysia Campus, Semenyih 43500, Malaysia; asad.rahman@nottingham.edu.my

² School of Engineering and Physical Science, Heriot-Watt University Malaysia, Putrajaya 62200, Malaysia; k.cheah@hw.ac.uk

* Correspondence: j.chin@hud.ac.uk; Tel.: +60-3-8924-8378

† These authors contributed equally to this work.

Received: 18 December 2017; Accepted: 7 March 2018; Published: 9 March 2018

Abstract: Ammonium Dinitramide (ADN) in its generic form has a long needle shaped structure, which hinders higher solid loading. Therefore, it is of utmost importance to optimize its crystal morphology into octagonal shapes. Moreover, the low critical humidity level of ADN renders it unusable in a humid climate. Hence, encapsulation with a hydrophobic polymer is necessary. In the present work, ADN was synthesized by nitration of potassium sulfamate with mixed acid nitration. The product was then mixed with toluene, graphene, citryl ammonium butyl, Cab-o-sil, and coating polymer (Polystyrene or HTPB) and treated with ultrasound to obtain semi-spherical ADN-coated particles. The method offers a reduction in operating temperature and elimination of ADN melting in the shape-altering process. In addition, the ADN product has a similar particle size and thermal stability compared to those in a conventional ADN melt-prilling method. The ADN product investigated under SEM confirms the particle morphological change from long needles into semi-spherical shapes. The particle size obtained, in the micrometer range, is ideal for higher theoretical maximum density. Furthermore, the ultrasound-treated ADN particles show significant reduction in moisture absorption, from 68% to 16% at 65% relative humidity. The DSC result shows no degradation of thermal stability of the coated particles.

Keywords: Ammonium Dinitramide (ADN); ultrasound sonication; green propellant; polymer coating

1. Introduction

The utility of Ammonium Dinitramide (ADN) as a highly energetic oxidizer has several advantages in terms of performance, stability [1], and environmental friendliness as compared to conventional Ammonium Perchlorate (AP)-based propellants [2]. However, solid grain casting of raw ADN is hindered by its needle shape [3] and by its high moisture absorption tendency and lower critical humidity level (55.2% RH). Previous experiments have shown that the moisture absorption of ADN is higher than that of AP [4]. The hygroscopicity of ADN can be decreased by coating it with hydrophobic polymers [3,5,6] such as hydroxyl terminated polybutadiene (HTPB), polystyrene (PS), and polyacrylate (PA). Otherwise, specifications given on the particle size, particle layout geometry, and surface area under the experimental conditions have seldom been described in the literature. These factors, i.e., particle morphology and water absorption [7], are known to reduce the Theoretical Maximum Density (TMD) and, consequently, the specific impulse of the ADN solid grain.

Many methods have been utilized to alter the crystal particle morphology of energetic materials, such as melt prilling [6], ultrasound-assisted crystallization [7], solvent crystallization [8], and spray

crystallization [9]. Melt prilling, which is an important process in conventional production of ADN, possesses several drawbacks, such as volumetric expansion in the melting phase and it being hazardous due to high operating temperature. In fact, ADN decomposes slowly in its molten condition, generating nitrous oxides [10,11] and creating cavities and fractures during solidification into the final grain. During solidification, a volumetric shrinkage of up to 14% creates foam on the surface of ADN grain [10].

The ultrasonic method is interesting as it acts as a source of mechanical energy, allowing us to reduce the ADN particle size and changing the crystal morphology. The importance of improving the crystal morphology can be highlighted by its ability to increase the specific impulse by 30% to 50% [12]. Successful modification of RDX crystal morphology by ultrasound was previously reported [9,13], but not for ADN. It is known that ultrasound treatment can induce oxidation reactions for many substrates, as reported in [14,15]. However, ADN does not undergo decomposition or oxidative reactions during such treatment, unless sodium hydroxide was added [16].

In this study, we investigate the use of an ultrasound sonication technique to alter the morphology and improve the hygroscopicity of the ADN particles. Scanning electron microscopy (SEM) is used to examine the change in morphology. From the SEM images, the change in particle shape can be observed, while the mean particle size can be measured. Water absorption tests were carried out to evaluate the effect of polymeric coating, i.e., PS and HTPB, on the hygroscopicity of the ADN particles. Finally, the thermal stability of the coated ADN particles are studied using differential scanning calorimetry (DSC).

2. Materials and Methods

2.1. ADN Synthesis

ADN used in this study was synthesized by nitration of potassium sulfamate with nitric acid and sulfuric acid at $-45\text{ }^{\circ}\text{C}$ [17,18].

First, potassium sulfamate was prepared in bulk by the neutralization of potassium hydroxide with sulfamic acid at stoichiometric ratios. The neutralized solution was concentrated to 50% volume in a rotary evaporator. It was then added into ethanol at a 1:2 ratio by volume to obtain precipitation. The precipitate of potassium sulfamate was filtered, washed with ethanol, dried overnight at $70\text{ }^{\circ}\text{C}$, and stored for use in further experiments.

In the second step, potassium sulfamate was nitrated with a mixture of nitric acid and sulfuric acid at $-45\text{ }^{\circ}\text{C}$ for 25 min. The nitration reaction was stopped by diluting it with crushed ice. Subsequently, the diluted mixture was neutralized by potassium hydroxide. The mixture was dried in a rotary evaporator at $60\text{ }^{\circ}\text{C}$. The dried powder was extracted with acetone and filtered. Then, 2-propanol was added into the acetone solution to obtain precipitation. The precipitation was filtered and discarded. The solution was evaporated in a rotary evaporator at $60\text{ }^{\circ}\text{C}$ to half of its initial volume. *n*-hexane was added into the solution until the precipitate of potassium dinitramide (KDN) was visible. The precipitated KDN is usually in the range of 80 to 90 wt % purity, as determined by UV spectroscopy. The KDN was then converted to ADN by reacting it with ammonium sulfate in water.

After the conversion to ADN, the entire solution was evaporated at $70\text{ }^{\circ}\text{C}$ to obtain dry powder. This dry powder was then extracted with ethyl acetate and collected. The collected ethyl acetate solution of ADN was then dried in a rotary evaporator to obtain pure ADN. The purity was determined by UV spectroscopy to be in range of 99 to 99.5 wt %.

2.2. Melt Prilling and Coating of Pristine ADN by Conventional Method

Melt prilled ADN samples were prepared according to the method given in [6]. Here, 0.5 g of dried pristine ADN was added in 50 mL paraffin oil, followed by the addition of 0.01 g (2 wt % w.r.t. ADN) Cab-o-sil at $100\text{ }^{\circ}\text{C}$ under strong agitation. The mixture was cooled to room temperature. The prilled ADN was then filtered and washed with *n*-hexane to remove traces of paraffin oil. The filtrate product of prilled ADN particles were then added to a mixture of polystyrene (PS) in 50 mL dichloromethane

and evaporated in a rotary evaporator to obtain coated ADN [6]. In the second experiment, PS was replaced with hydroxyl-terminated polybutadiene (HTPB).

2.3. Prilling and PS Coating of Pristine ADN Particles by Ultrasound Sonication

Here, 0.5 g ADN particles were added to 50 mL of toluene mixture, which also included 0.01 g Cab-o-Sil (2 wt % w.r.t. ADN), 0.01 g cetyltrimethylammonium bromide (CTAB) (2 wt % w.r.t. ADN), 0.01 g graphene powder (Graphene Nano powder, 8 nm flakes AO-2, Graphene Supermarket, Calverton, NY, USA) (2 wt % w.r.t. ADN), and 0.025 g PS (5 wt % w.r.t. ADN). The mixture was then sonicated (Elmasonic P, Elma, Singen, Germany) for 60 min at 60 °C at 37 kHz in a glass test tube. After sonication, the mixture was poured into a beaker containing 100 mL of *n*-hexane at room temperature and again sonicated for 5 min to avoid particle agglomeration. Then, the mixture was evaporated at 45 °C under vacuum to obtain ADN particles coated with PS. The experimental setup is shown in Figure 1. The experiments were repeated by replacing toluene with dichloromethane, *n*-hexane and petroleum ether but were all unsuccessful due to poor dissipation of ADN particles and evaporation during sonication.

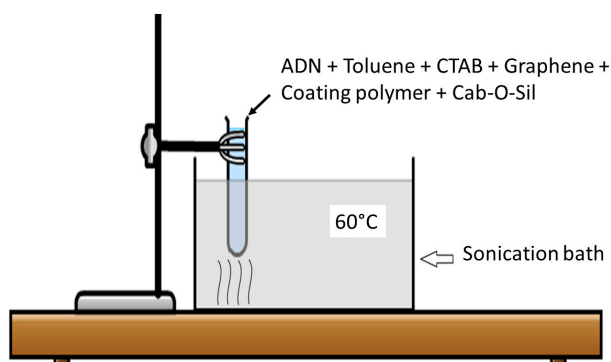


Figure 1. Experimental setup of Ammonium Dinitramide (ADN) sonication. Pristine ADN particles sonicated in toluene mixture.

2.4. Prilling and HTPB Coating of Pristine ADN Particles by Ultrasound Sonication

Toluene mixture was prepared according to the same procedures in Section 2.3 without the adding of PS. An HTPB mixture, which consisted of toluene diisocyanate (TDI), glycerol, and HTPB monomer, was prepared separately. Composition of the mixture is given in Table 1. The HTPB mixture was added into the toluene mixture together with ADN particles.

Table 1. Composition of hydroxyl terminated polybutadiene (HTPB) in toluene mixture.

Chemical Name	Function	Weight %
TDI	Crosslinker [19]	10
Glycerol	Catalyst	10
HTPB monomer	Monomer	80

The mixture was then sonicated for 60 min at 60 °C at 37 kHz in a glass test tube. After sonication, the mixture was poured into a beaker containing 100 mL *n*-hexane at room temperature and then the mixture was evaporated at 70 °C (boiling point of *n*-hexane is 68 °C) under vacuum to obtain ADN particles coated with HTPB. A higher temperature of 70 °C was used to cure the HTPB.

2.5. Morphology and Thermal Stability

The coated ADN samples were kept at room temperature in a humidity-controlled chamber with 20% relative humidity (RH). During the particle shape analysis under SEM (Quanta400F, FEI,

Hillsboro, OR, USA), the use of high energy radiation and high zoom levels were avoided as they may cause decomposition in the ADN samples. The thermal characteristics of the samples were analyzed by DSC (Mettler Toledo 1 STAR, Mettler Toledo, Greifensee, Switzerland) of 35 °C to 300 °C at 10 °C min^{−1} heating rate with a nitrogen gas purge.

2.6. Water Absorption Test

The moisture absorption tests were performed by placing 0.3 to 0.5 g of the sample in an enclosed environment with a uniform airflow rate of 5 L min^{−1}. The humidity of the chamber was maintained at 65 ± 2% RH [20] by passing the air from a saturated solution of ammonium nitrate (AN). The weight of the sample was recorded at 60 min intervals for a total period of 240 min to determine the water absorption. The experimental setup is shown in Figure 2.

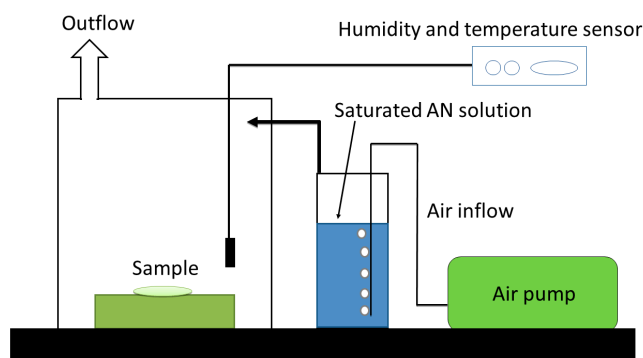


Figure 2. Experimental setup for moisture absorption test. The sample is in an enclosed container exposed to wet air and weighted periodically.

3. Results and Discussion

The main objective of these experiments was to increase the density ADN particles by altering the morphology of pristine ADN particles into spherical particles and to add an effective hydrophobic polymer coating. The conventional prilling method involves the melting of ADN. This could pose a potential safety hazard as the energetic ADN particles may decompose during the prilling process. Therefore, the new method based on ultrasound treatment was utilized for alteration of ADN crystal morphology and hydrophobic polymer coating. The main criterion for the ultrasound treatment of ADN was the selection of a suitable sonication medium. First, an organic solvent, which has no solubility toward ADN but has solubility toward the coating polymer, was highly desirable. Secondly, the boiling point of the solvent needed to be sufficiently high to sustain the ultrasound treatment without evaporation. In addition, the solvent needed to be removed easily by vacuum evaporation. This was necessary because excess solvent has to be removed without exposure to atmosphere.

3.1. Selection of Sonication Medium and Polymer

The reduction in particle size is dependent on the surface energy of solids (σ) [21]. The interfacial tension (γ) is the measure of interfacial energy between two immiscible fluids, or solid-fluid, given as [21]

$$\gamma_{12} = \gamma_1 + \gamma_2 - 2(\gamma_1^d \cdot \gamma_2^d)^{\frac{1}{2}} \quad (1)$$

Equation (1) is termed the Fowkes correlation, where γ_{12} is the interfacial tension and γ_1^d and γ_2^d refer to dispersion forces to the surface tension by liquid 1 and liquid 2, respectively [21]. In this case, materials 1 and 2 would be the combinations of ADN, toluene, PS, and graphene with each other, as shown in Table 2.

However, the value of dispersion forces can be assumed to be 1, giving [22]

$$\gamma_{12} \approx \left(\gamma_1^{\frac{1}{2}} - \gamma_2^{\frac{1}{2}} \right)^2 \quad (2)$$

The relation between surface tension and solubility parameter (δ) is given as [23]

$$\delta = 4.1(\gamma/V^{1/3})^{0.43} \quad (3)$$

where V is equivalent to volume.

Furthermore, the interfacial energy is affected by crystal structure of the prilled and coated ADN. The wetting is favored if the surface energy of solid is higher than surface tension of liquid [23]. The surface tension of ADN melt ($\gamma = 89$ mN/m) [21] is very high due to hydrogen bonding and polarity, compare to water = 72 mN/m, while toluene has a surface tension of $\sigma = 28.4$ mN/m. The surface tension of the ADN melt was used to estimate surface energy of the ADN solid.

Based on the bond breaking rule proposed in the previous literature [24], the surface tension $\gamma_{liquid}(ADN \text{ melt})$ can be correlated to surface energy by the following equation:

$$\sigma_{solid} \cong \frac{\gamma_{liquid}}{0.713} \quad (4)$$

Thus, the surface energy of ADN solid is estimated to be $\sigma_{ADN} = 124.8$ mN/m.

The difference in surface tension hence favors proper wetting and dispersion of ADN in toluene, which is further enhanced by elevated temperature i.e., 60 °C. The addition of cationic surfactant, CTAB, with an estimated hydrophilic-lipophilic balance (HLB) equivalent number 13+ [25], failed to disperse the ADN in solvents except toluene. The application of ultrasound sonication facilitates rapid dispersion, which increases the solid-liquid interface.

Using the value of σ_{ADN} , the interaction force between different components of the system were calculated as shown below (Table 2) with data from Krevelen [23]. In general, the adding of ADN increases the interface energy with ADN-toluene combination that exhibits the highest interface energy.

Table 2. Interface energy of different components calculated using Equation (2).

Interface Components	Interface Energy
ADN-toluene	$\gamma_{ADN-TI} = 34.7$ mN/m
ADN-PS	$\gamma_{ADN-PS} = 22.01$ mN/m
ADN-graphene	$\gamma_{ADN-gr} = 18.82$ mN/m
Toluene-PS	$\gamma_{TI-PS} = 1.43$ mN/m
Toluene-graphene	$\gamma_{TI-PS} = 2.40$ mN/m
Graphene-PS	$\gamma_{gr-PS} = 0.124$ mN/m

The PS and graphene adhesion to ADN can be described by the work of adhesion as given by

$$W_{adh} = \gamma_{s1} + \gamma_{s2} - \gamma_{s1s2} \quad (5)$$

$$\text{where, } \gamma_{s1s2} = \left((\gamma_{s1})^{\frac{1}{2}} + (\gamma_{s2})^{\frac{1}{2}} \right)^{\frac{1}{2}}$$

where γ_{s1} and γ_{s2} are surface energy of materials being considered.

A negative value of W_{adh} represents poor adhesion and reversibility of the process. W_{adh} values for different components of the system are shown in Table 3. They are all in the positive regime. This implies a good adhesion of ADN to PS ($W_{adn-ps} = 144.81$ mN/m). Similarly, using the interface energy of $\gamma_{gr} = 46.7$ mN/m [26], adhesion of graphene toward ADN and PS was calculated

to be $W_{adn-gr} = 169.11 \frac{mN}{m}$ and $W_{gr-ps} = 88.57 \frac{mN}{m}$, respectively, suggesting a good compatibility among them.

Table 3. Work of adhesion for different components of the system.

Components	Work of Adhesion
ADN-PS	$W_{adn-ps} = 144.81 \text{ mN/m}$
ADN-graphene	$W_{adn-gr} = 169.11 \text{ mN/m}$
PS-graphene	$W_{ps-gr} = 88.57 \text{ mN/m}$

3.2. Crystal Morphology and Particle Size

Pristine ADN synthesized in this experiment has long needle-like shape, as shown in Figure 3, compared to pristine ADN prepared by Heintz et al. [6]. Spherical ADN particles produced via ultrasound sonication followed by coating with 5% PS and HTPB are shown in Figure 4. In comparison, ADN melt prilled with conventional method and coated with 5 wt % PS is shown in Figure 5. The particle diameters were measured from the SEM images using MATLAB.

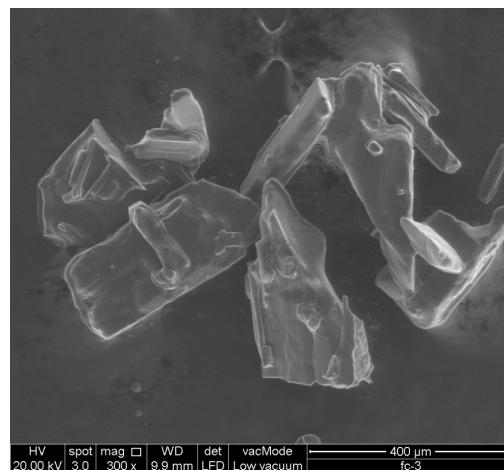


Figure 3. Scanning electron microscopy (SEM) image of pristine ADN used in these experiments.

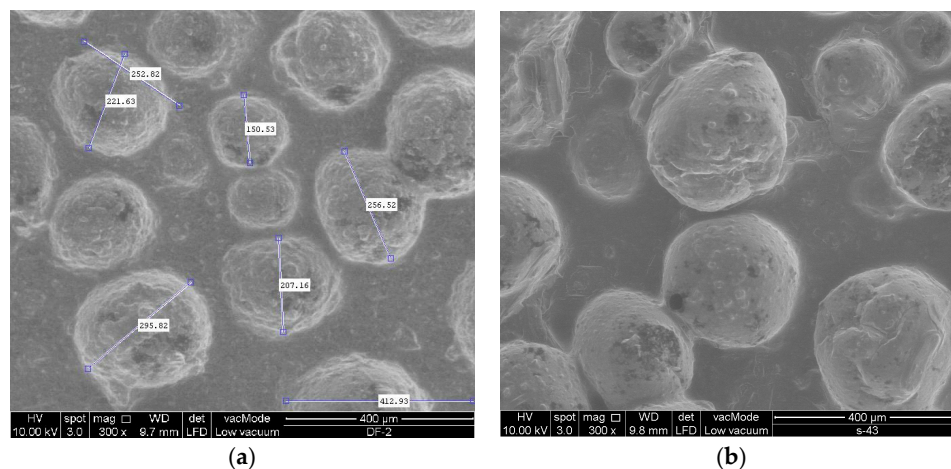


Figure 4. (a) SEM image of ADN produced via ultrasound sonication, following by coating with 5% of PS. The particles diameter ranges from 150 μm to 295 μm; (b) SEM image of ADN sonicated and coated with HTPB. The particle diameter ranges from 155 μm to 305 μm.

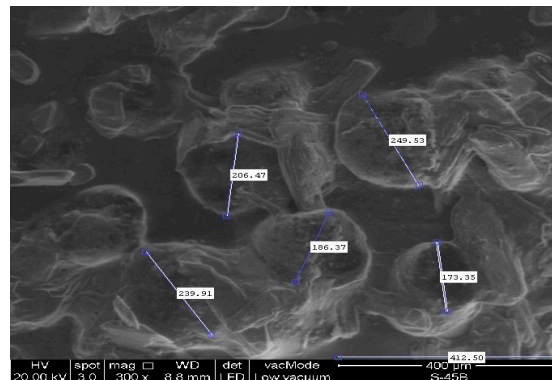


Figure 5. SEM image of ADN produced by melt prilling and coating with 5 wt % polystyrene (PS).

In Figure 5, the melt prilled ADN particle coating with 5 wt % PS has a size within the range of 173–250 μm . Overall, the ADN particles produced using this method have a mean diameter of $231 \pm 48 \mu\text{m}$. For ultrasound sonication, the ADN particles have a spherical shape with a particle diameter that ranges from 150 μm to 295 μm , with an overall mean diameter of $225 \pm 30 \mu\text{m}$. Although the existing ultrasonication set-up could not reduce the mean particle size of the coated ADN particles substantially, it reduced the diameter to the smallest dimension of 150 μm . This is approximately 13% smaller than its counterpart produced using the prilling method. This suggests the ultrasonication method can be optimized further. Nevertheless, the spherical shape of the coated ADN particles produced using the ultrasonication method enables a higher packing density.

3.3. Water Absorption Testing

The water absorption testing was carried out using pristine ADN, prilled ADN and sonicated ADN particles, respectively. The mass gain in the samples are shown in Figure 6. In general, the high water absorption in ADN particles is due to the presence of a hydrogen bond in its crystal structure. It is obvious from Figure 6 that the prilling and sonicated coating of ADN has reduced the water absorption as compared to pristine ADN. ADN particles sonicated coating with 5 wt % of PS achieved up to 30% in mass gain after 240 min, while sonicated coating with the identical concentration of HTPB reached only 18% of mass gain. The testing of ADN coated with hydrophobic PS embedded with graphene flakes shows a reduction in moisture absorption. This effect is particularly significant after prolonged duration, i.e., 240 min. The graphene is a hydrophobic material [26] and acts as moisture barrier because of its high aspect ratio [27,28].

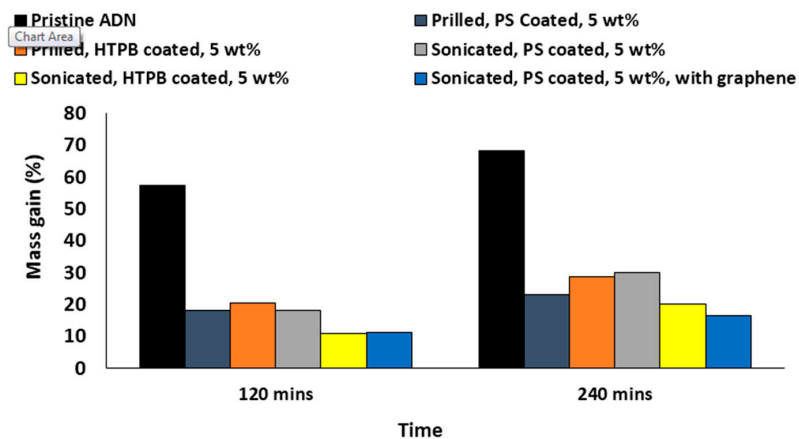


Figure 6. Mass gain in pristine ADN, melt prilled, and sonicated coating of the ADN particle.

3.4. Effect of Additives

Several attempts were made to produce coated ADN without graphene, CTAB, and Cab-o-sil. In the absence of CTAB, approximately 70% of prilled ADN was still left at the bottom of the toluene mixture even after 180 min of sonication. In another attempt to produce coated ADN without graphene and Cab-o-sil, the prilled ADN particles agglomerated in the drying and evaporation steps.

CTAB consists of an anionic long carbon chain (19 carbons) and a relatively weak methylammonium bromide cation, which makes it cationic surfactant [29].

The cationic part attracts ADN because of the overall negative charge of ADN molecules. Furthermore, the anionic part of CTAB attracts methyl pendant group of toluene by virtue of partial charges leading to proper suspension of ADN in toluene.

In this work, Cab-o-sil was added as a protective colloid to promote emulsification and reduction in viscosity [30]. Its non-Newtonian behaviour provides better mechanical energy transfer to surface boundary between toluene and ADN particles. In addition, it also decreases the agglomeration of particles by inducing steric hindrance [30]. In this case, the mechanical energy required to reduce the ADN particle size is provided by the ultrasound sonication.

The use of graphene in energetic materials is a rather new idea. It has only been reported for a few propellants with improvements in thermal stability [31]. However, it has been used extensively to impart hydrophobic properties in polymers, where it acts as a physical barrier or produces a lotus effect [31] to reduce moisture absorption. As such, graphene was added into the ADN suspension during sonication to reduce moisture absorption. In addition, the adding of graphene is expected to reduce agglomeration of the ADN particles by increasing the distance between ADN particles. Figure 7 shows the SEM image of the agglomeration of ADN particles without the adding of graphene.

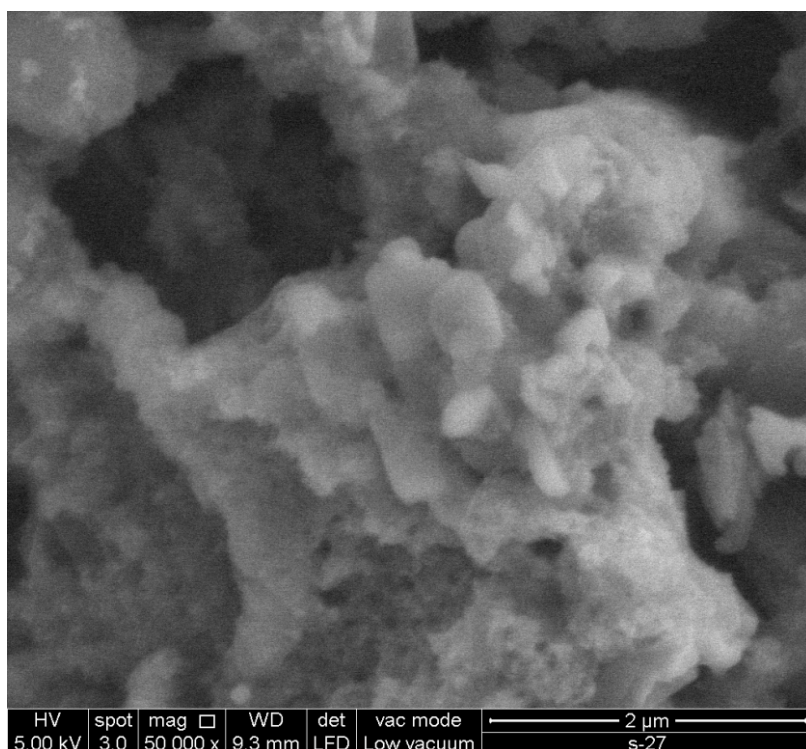


Figure 7. Agglomeration of ADN particles.

3.5. Thermal Analysis

DSC results of pristine, prilled, and sonicated ADN samples are shown in Figure 8. Pristine and prilled ADN particles were reported to have two peaks in the range of 130 to 220 °C [32,33]. The first

peak around 130 °C indicates the decomposition of the dinitramide ion to produce ammonium nitrate and N₂O. The second peak, which is minor peak compared to the first, indicates decomposition of ammonium nitrate [33]. All of our samples exhibit the similar trend of having two peaks. The coating of HTPB and PS on ADN particles has shifted the second peak to the range of 180 to 230 °C. Higher content of HTPB (20 wt %) causes slow burning of ADN sample. Thus, it has the first peak (at 200 °C) in higher temperature as compared to the other peaks. The trend in the DSC result for sonicated ADN particles is similar to the that of pristine and prilled ADN particles. This indicates that the technique used to coat the ADN particles has a negligible effect on the thermal properties of ADN particles. However, an exception was observed for sonicated ADN particles with 20 wt % HTPB. It has higher melting temperature due to the increased amount of HTPB, contributing to the delay in burning. The overall heat release (enthalpy) during decomposition is 1.78–3.35 kJ/g (220–416 kJ/mol), which is in good agreement with published values [34–36]. A summary of the results from thermal analysis is tabulated in Table 4.

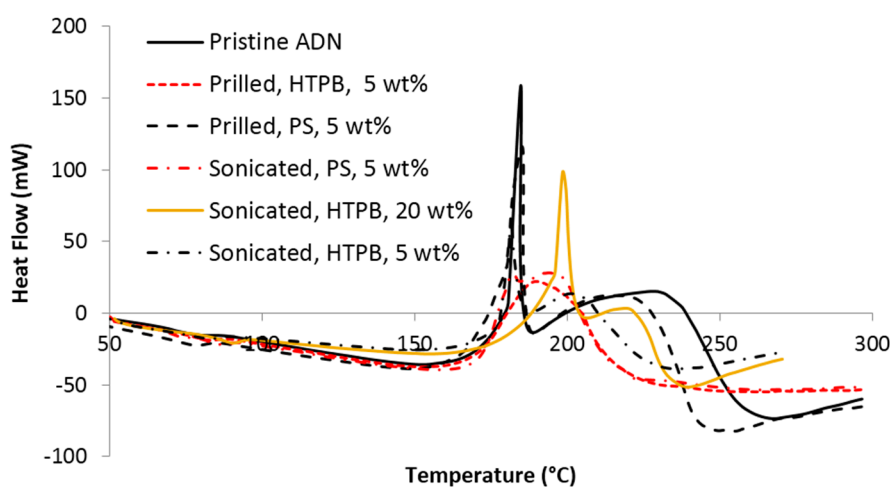


Figure 8. Thermal decomposition in differential scanning calorimetry (DSC) obtained for samples at 10 °C min^{−1} heating rate.

Table 4. Details of thermal testing.

Sample Type	Decomposition Onset Temperature (°C)	Enthalpy of Decomposition (kJ/g)	Maximum Peak Temperature (°C)
Pristine ADN	177	1.86	193
Prilled, PS, 5 wt %	181	3.35	186
Prilled, HTPB, 5 wt %	170	2.19	190
Sonicated, PS, 5 wt %	171	1.81	192
Sonicated, HTPB, 5 wt %	178	1.78	181
Sonicated, HTPB, 20 wt %	196	2.62	198
Pristine ADN [30]	126	1.97	159
Prilled ADN [37]	168	2.01	195

4. Conclusions

In this work, a method for the prilling and coating of ADN particles in an organic solvent using ultrasound sonication was demonstrated. The demonstrated method is suitable for the production of ADN particles in highly humid conditions because ADN is not exposed to atmosphere throughout the process. The morphology of the particle has changed to semi-spherical. The particle size obtained is comparable to the melt prilling method. The combination of Cab-o-sil, CTAB, and graphene and HTPB provides good adhesion on the pristine ADN particles. The resulting hydrophobic coating has reduced the water absorption of the ADN particles. The ultrasound sonicated coating method does

not change the thermal stability of the particles. This method should provide an alternative route in the production of densely packed ADN particles for use in space propulsion systems.

Acknowledgments: This work was supported by eScience Fund from Ministry of Science, Technology and Innovation Malaysia (MOSTI), Project number: 04-02-12-SF0160.

Author Contributions: All authors contributed to experimental design and data analysis. Asad Rahman performed the experiments and wrote the paper. Jitkai Chin contributed to project overview. Kean How Cheah contributed to data analysis and manuscript writing.

Conflicts of Interest: The authors declare no conflict of interest. The founding sponsors had no role in the design of the study; in the collection, analyses, or interpretation of data; in the writing of the manuscript, and in the decision to publish the results.

References

1. Luk'yanov, O.A.; Tartakovsky, V.A. Synthesis and Characterization of Dinitramidic Acid and Its Salts. In *Solid Propellant Chemistry, Combustion, and Motor Interior Ballistics*; Brill, T.B., Ren, W.-Z., Zarchan, P., Yang, V., Eds.; American Institute of Aeronautics and Astronautics: Washington, DC, USA, 2000; Volume 185, pp. 207–219, ISBN-13 978-1563474422.
2. Nagamachi, M.Y.; de Oliveira, J.S.I.; Kawamoto, A.K.; de Dutra, R.L. AND—The new oxidizer around the corner for an environmentally friendly smokeless propellant. *J. Aerosp. Technol. Manag.* **2009**, *1*, 153–160. [[CrossRef](#)]
3. Östmark, H.; Bemm, U.; Langlet, A.; Sanden, R.; Wingborg, N. The properties of ammonium dinitramide (ADN): Part 1, basic properties and spectroscopic data. *J. Energ. Mater.* **2000**, *18*, 123–138. [[CrossRef](#)]
4. Cui, J.; Han, J.; Wang, J.; Huang, R. Study on the Crystal Structure and Hygroscopicity of Ammonium Dinitramide. *J. Chem. Eng. Data* **2010**, *55*, 3229–3234. [[CrossRef](#)]
5. Ramaswamy, A. Energetic-material combustion experiments on propellant formulations containing prilled ammonium dinitramide. *Combust. Explos. Shock Waves* **2000**, *36*, 119–124. [[CrossRef](#)]
6. Heintz, T.; Pontius, H.; Aniol, J.; Birke, C.; Leisinger, K.; Reinhard, W. Ammonium Dinitramide (ADN)—Prilling, Coating, and Characterization. *Propellants Explos. Pyrotech.* **2009**, *34*, 231–238. [[CrossRef](#)]
7. Bayat, Y.; Zeynali, V. Preparation and Characterization of Nano-CL-20 Explosive. *J. Energ. Mater.* **2011**, *4*, 281–291. [[CrossRef](#)]
8. Fuhr, F.I. Crystallization of the Energetic Oxidizer Salt Ammonium Dinitramide: Theoretical and Experimental Considerations. Ph.D. Thesis, Martin Luther University, Halle-Wittenberg, Germany, 2008.
9. Teipel, U. Production Particles of Explosives. *Propellants Explos. Pyrotech.* **1999**, *24*, 134–139. [[CrossRef](#)]
10. Hahma, A.; Edvinsson, H.; Östmark, H. The Properties of Ammonium Dinitramide(ADN): Part 2: Melt Casting. *J. Energ. Mater.* **2010**, *28*, 114–138. [[CrossRef](#)]
11. Östmark, H.; Helte, A.; Karlsson, S.; Hahma, A.; Edvinsson, H. Detonation Properties and Reaction Rate Modeling of Melt Cast Ammonium Dinitramide (ADN). In *Proceedings of the 12th International Detonation Symposium*, San Diego, CA, USA, 11–16 August 2002; pp. 775–780.
12. Larson, A.; Wingborg, N. Green Propellants Based on Ammonium Dinitramide (ADN). In *Advances in Spacecraft Technologies*; Hall, J., Ed.; Slavka Krautzeka: Rijeka, Croatia, 2011; ISBN 978-953-307-551-8.
13. Kim, J.-W.; Shin, M.-S.; Kim, J.K.; Kim, H.S.; Koo, K.K. Evaporation Crystallization of RDX by Ultrasonic Spray. *Ind. Eng. Chem. Res.* **2011**, *50*, 12186–12193. [[CrossRef](#)]
14. Kuppa, R.; Moholkar, V.S. Physical features of ultrasound-enhanced heterogeneous permanganate oxidation. *Ultrason. Sonochem.* **2010**, *17*, 123–131. [[CrossRef](#)] [[PubMed](#)]
15. Malani, R.S.; Moholkar, V.S.; Choudhury, H.A. Acid catalyzed biodiesel synthesis from Jatropha oil: Mechanistic aspects of ultrasonic intensification. *Chem. Eng. J.* **2013**, *31*, 262–272. [[CrossRef](#)]
16. Qadir, L.R.; Osburn-Atkinson, E.J.; Swider-Lyons, K.E.; Cepak, V.M.; Rolison, D.R. Sonochemically induced decomposition of energetic materials in aqueous media. *Chemosphere* **2003**, *50*, 1107–1114. [[CrossRef](#)]
17. Wingborg, N. Ammonium Dinitramide-Water: Interaction and Properties. *J. Chem. Eng. Data* **2006**, *51*, 1582–1586. [[CrossRef](#)]
18. Langlet, A.; Östmark, H.; Wingborg, N. Method of Preparing Dinitramidic Acid and Salts Thereof. U.S. Patent 5,976,483, 8 August 1999.

19. Kohga, M. From Cross-linking to Plasticization—Characterization of Glycerin/HTPB Blends. *Propellants Explos. Pyrotech.* **2009**, *34*, 436–443. [CrossRef]
20. Wexler, A. Practical Laboratory Data. In *CRC Handbook of Chemistry and Physics*; Lide, D.R., Ed.; CRC Press: New York, NY, USA, 2003.
21. Teipel, U.; Heintz, T. Surface Energy and Crystallization Phenomena of Ammonium Dinitramide. *Propellants Explos. Pyrotech.* **2005**, *30*, 404–411. [CrossRef]
22. Agrawal, A. Surface Tension of Polymers. Available online: <http://web.mit.edu/nmf/education/wettability/summerreading-2005short.pdf> (accessed on 12 June 2017).
23. Van Krevelen, D.W.; Nijenhuis, K.T. *Properties of Polymers*, 4th ed.; Elsevier: Amsterdam, The Netherlands, 2009; ISBN 9780080548197.
24. Aqra, F.; Ayyad, A. Surface energies of metals in both liquid and solid states. *Appl. Surf. Sci.* **2011**, *257*, 6372–6379. [CrossRef]
25. ICI Americas Inc. The HLB System: A Time-Saving Guide to Emulsifier Selection. Available online: http://www.firp.ula.ve/archivos/historicos/76_Book_HLB_ICI.pdf (accessed on 12 June 2017).
26. Wang, S.; Zhang, Y.; Abidi, N.; Cabrales, L. Wettability and Surface Free Energy of Graphene Films. *Langmuir* **2009**, *25*, 11078–11081. [CrossRef] [PubMed]
27. Chang, K.; Hsu, M.; Lu, H.; Lai, M.; Liu, P.; Hsu, C.; Ji, W.; Chuang, T.; Wei, Y.; Yeh, J.; et al. Room-temperature cured hydrophobic epoxy/graphene composites as corrosion inhibitor for cold-rolled steel. *Carbon* **2014**, *66*, 144–153. [CrossRef]
28. Luechinger, N.A.; Athanassiou, E.K.; Strak, W.J. Graphene-stabilized copper nanoparticles as an air-stable substitute for silver and gold in low-cost ink-jet printable electronics. *Nanotechnology* **2008**, *19*, 445201. [CrossRef] [PubMed]
29. Smith, D.K.; Korgel, B.A. The importance of the CTAB surfactant on the colloidal seed-mediated synthesis of gold nanorods. *Langmuir* **2008**, *24*, 44–649. [CrossRef] [PubMed]
30. Teipel, U.; Heintz, T.; Krause, H. Crystallization of Spherical Ammonium Dinitramide (ADN) particles. *Propellants Explos. Pyrotech.* **2000**, *25*, 81–85. [CrossRef]
31. Sabourin, J.L.; Dabbs, D.M.; Yetter, R.A.; Dryer, F.L.; Aksay, I.A. Functionalized Graphene Sheet Colloids for Enhanced Fuel/Propellant Combustion. *ACS Nano* **2009**, *3*, 3945–3954. [CrossRef] [PubMed]
32. Yang, R.; Thakre, P.; Yang, V. Thermal Decomposition and Combustion of Ammonium Dinitramide (review). *Combust. Explos. Shock Waves* **2005**, *41*, 657–679. [CrossRef]
33. Matsunaga, H.; Habu, H.; Atsumi, M. Thermal behavior of new oxidizer ammonium dinitramide. *J. Therm. Anal. Calorim.* **2012**, *111*, 1183–1188. [CrossRef]
34. Jones, D.; Kwok, W.S.M.; Vachon, M.; Badeen, C.; Ridley, W. Characterization of ADN and ADN-Based Propellants. *Propellants Explos. Pyrotech.* **2005**, *30*, 140–147. [CrossRef]
35. Vyazovkin, S.; Wight, C.A. Ammonium Dinitramide: Kinetics and Mechanism of Thermal Decomposition. *J. Phys. Chem.* **1997**, *101*, 5653–5658. [CrossRef]
36. Bottaro, J.C.; Penwell, E.P.; Schmitt, R.J. 1,1,3,4-Tetraoxo-1,2,3-triazapropene Anion, a New Oxy Anion of Nitrogen: The Dinitramide Anion and Its Salts. *Am. Chem. Soc.* **1997**, *119*, 9405–9410. [CrossRef]
37. Tompa, A.S. Thermal analysis of ammonium dinitramide (ADN). *Thermochim. Acta* **2000**, *357*, 177–193. [CrossRef]



© 2018 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).